

## Bonding of Metals to Carbon Rings: $\text{LaC}_n^+$ Isomers with $\text{La}^+$ Inserted and Attached to the Ring

David E. Clemmer, Konstantin B. Shelimov, and Martin F. Jarrold\*

Department of Chemistry, Northwestern University  
2145 Sheridan Road, Evanston, Illinois 60208


Received February 7, 1994

Revised Manuscript Received April 12, 1994

Doping carbon clusters with metal atoms provides an intriguing way to modify their properties and generate new materials. The metallofullerenes<sup>1,2</sup> and metallocarbohedranes<sup>3,4</sup> are good examples. Despite the intense interest in these systems, there is virtually no experimental information about how a metal atom binds to a carbon cluster, even in simple model systems. In this communication we describe studies of small ( $n = 12\text{--}40$ )  $\text{LaC}_n^+$  clusters and report the observation of two families of  $\text{LaC}_n^+$  monocyclic rings. For clusters with an even number of carbon atoms, an isomer where the lanthanum atom appears to be inserted into the ring dominates, while for odd-numbered clusters, only isomers where the lanthanum appears to be attached to the outside (or inside) of the carbon ring are observed. The odd/even fluctuations in the relative abundances of the two isomers provide an important clue about the nature of the chemical bonding in these clusters. This information is necessary to unravel the mechanism of endohedral metallofullerene synthesis, since recent studies have shown that  $\text{LaC}_{60}^+$  polycyclic rings can be annealed into the endohedral metallofullerene with near unit efficiency.<sup>5</sup>

The apparatus and experimental techniques have been described in detail previously.<sup>6</sup>  $\text{LaC}_n^+$  ions generated by pulsed laser vaporization of a  $\text{La}_2\text{O}_3$ /graphite composite rod<sup>1</sup> were size selected with a quadrupole mass spectrometer. Fifty-microsecond pulses of mass-selected ions were then injected into a drift tube containing  $\sim 5$  Torr of helium. When the ions enter the drift tube they experience a rapid transient heating cycle as their injection energy is thermalized by collisions with the buffer gas. At high injection energies, the clusters may be heated to the point where they anneal or even fragment.<sup>7</sup> Further collisions with the buffer gas rapidly cool the clusters. They then travel across the drift tube under the influence of a weak electric field. The drift time depends on the structure of the cluster, such that clusters with compact geometries have shorter drift times than clusters with less compact geometries.<sup>8</sup> After exiting the drift tube the ions are focused into a second quadrupole mass spectrometer that is used to monitor the fragmentation pattern and transmit only the ion of interest.

The results presented here were recorded with an injection energy of 150 eV. At this energy a considerable amount of annealing and some fragmentation (usually less than 10%) occurs as the ions enter the drift tube. Thus, the drift time distributions of the surviving parent ions are dominated by relatively stable isomers.<sup>9</sup> Figure 1 shows drift time distributions recorded for  $\text{LaC}_{20}^+$ ,  $\text{LaC}_{21}^+$ ,  $\text{LaC}_{22}^+$ , and  $\text{LaC}_{23}^+$ .<sup>10</sup> Clusters containing even numbers of carbon atoms ( $\text{LaC}_{2n}^+$ ) show two relatively large peaks, while odd-numbered clusters ( $\text{LaC}_{2n+1}^+$ ) show only one. As the number of carbon atoms increases, the drift times become

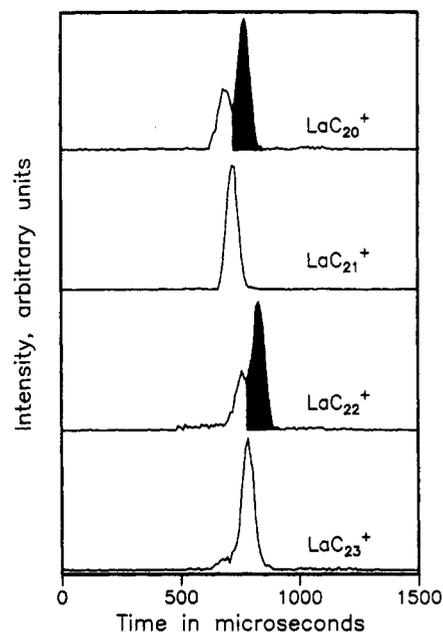

**Figure 1.** Drift time distributions recorded for  $\text{LaC}_{20}^+$ ,  $\text{LaC}_{21}^+$ ,  $\text{LaC}_{22}^+$ , and  $\text{LaC}_{23}^+$  at an injection energy of 150 eV. Clusters containing an even number of carbon atoms display two peaks while the odd-numbered clusters show only one. The shaded peak for the even clusters corresponds to the isomers assigned in the text to slow rings. The other nonshaded peaks correspond to isomers that we assign to fast rings. See the text for a discussion of the geometries. The small feature at shorter times in the drift time distribution for  $\text{LaC}_{23}^+$  is assigned to a bicyclic ring. The bicyclic rings appear to anneal into monocyclic rings as the injection energy is increased.

systematically larger because of the increase in the physical size of the cluster. The results in Figure 1 show that the smaller peak at shorter drift times for the  $\text{LaC}_{2n}^+$  clusters correlates with the single peak observed for  $\text{LaC}_{2n+1}^+$  clusters, while the larger peak at longer times for  $\text{LaC}_{2n}^+$  clusters is not present in the data for the  $\text{LaC}_{2n+1}^+$  clusters.

The basic patterns displayed in Figure 1 for the even- and odd-numbered clusters are observed over the entire 12-40-atom size range, although for even-numbered clusters above  $\text{LaC}_{26}^+$  the relative intensity of the shorter-time peak is too small to clearly distinguish it from the larger peak at longer times. As discussed below, we assign these two sets of peaks to fast and slow monocyclic rings. Slow rings are observed only for  $\text{LaC}_{2n}^+$  clusters, while fast rings are observed for both  $\text{LaC}_{2n}^+$  and  $\text{LaC}_{2n+1}^+$  clusters, but dominate for  $\text{LaC}_{2n+1}^+$ . For  $\text{LaC}_{12}^+$ – $\text{LaC}_{24}^+$  clusters, the fast and slow rings are the only isomers present in significant abundance. For larger clusters additional peaks appear at shorter times. These include peaks that we attribute to bicyclic rings and metallofullerenes. The metallofullerenes dominate the isomer distribution for clusters larger than  $\text{LaC}_{34}^+$ . We have studied these small metallofullerenes in some detail and will discuss them elsewhere.<sup>11</sup> The bicyclic rings first emerge at around  $\text{LaC}_{23}^+$  (which is roughly the size that this isomer emerges for pure carbon clusters<sup>8</sup>). The bicyclic rings appear to anneal into monocyclic rings, as has been observed for the pure carbon clusters.<sup>12,13</sup>

Figure 2 shows the inverse mobilities determined for the two components in the drift time distributions plotted against cluster

(1) Heath, J. R.; O'Brien, S. C.; Zhang, Q.; Liu, Y.; Curl, R. F.; Kroto, H. W.; Tittel, F. K.; Smalley, R. E. *J. Am. Chem. Soc.* **1985**, *107*, 7779.

(2) For a recent review, see: Bethune, D. S.; Johnson, R. D.; Salem, J. R.; deVries, M. S.; Yannoni, C. S. *Nature* **1993**, *366*, 123.

(3) Wei, S.; Guo, B. C.; Purnell, J.; Buzza, S.; Castleman, A. W., Jr. *Science* **1992**, *255*, 818.

(4) Pilgrim, J. S.; Duncan, M. A. *J. Am. Chem. Soc.* **1993**, *115*, 6958.

(5) Clemmer, D. E.; Shelimov, K. B.; Jarrold, M. F. *Nature* **1994**, *367*, 718.

(6) Jarrold, M. F.; Bower, J. E. *J. Chem. Phys.* **1992**, *96*, 9180.

(7) Jarrold, M. F.; Honea, E. C. *J. Phys. Chem.* **1991**, *95*, 9181.

(8) von Helden, G.; Hsu, M.-T.; Kemper, P. R.; Bowers, M. T. *J. Chem. Phys.* **1991**, *95*, 3835.

(9) Although the drift time distributions vary with cluster size, in general at low injection energies a larger abundance of isomers that we attribute to  $\text{LaC}_n^+$  bicyclic rings is observed.

(10) Several other peaks in addition to those shown in Figure 1 were often apparent in the measured drift time distributions. These additional peaks are assigned to doubly charged ions and/or ions that do not have the elemental composition  $\text{LaC}_n^+$  (as deduced from studies performed as a function of the  $\text{LaC}_n^+$  isotope distribution). For clarity we have removed the peaks in the drift time distributions shown in Figure 1 that do not result from  $\text{LaC}_n^+$  ions.

(11) Shelimov, K. B.; Clemmer, D. E.; Jarrold, M. F. Manuscript in preparation.

(12) Hunter, J.; Fye, J.; Jarrold, M. F. *J. Phys. Chem.* **1993**, *97*, 3460.

